

Orbital ordering in charge transfer insulators

M. V. Mostovoy and D. I. Khomskii

*Materials Science Center, University of Groningen,
Nijenborgh 4, 9747 AG Groningen, The Netherlands*

(Dated: February 2, 2008)

We discuss a new mechanism of orbital ordering, which in charge transfer insulators is more important than the usual exchange interactions and which can make the very type of the ground state of a charge transfer insulator, i.e. its orbital and magnetic ordering, different from that of a Mott-Hubbard insulator. This purely electronic mechanism allows us to explain why orbitals in Jahn-Teller materials typically order at higher temperatures than spins, and to understand the type of orbital ordering in a number of materials, e.g. K_2CuF_4 , without invoking the electron-lattice interaction.

PACS numbers: 75.30.Et, 72.80.Ga, 71.20.Be

Since the seminal Zaanen, Sawatzky, and Allen paper [1], it is widely accepted that strongly correlated insulators can be divided into two classes according to the nature of their gap. The Mott-Hubbard insulators (MHI) are characterized by the lowest-energy excitations of the type $d^n + d^n \rightarrow d^{n-1} + d^{n+1}$, obtained by transferring a d -electron from one transition metal (TM) ion to another, whereas in charge transfer insulators (CTI) the corresponding excitations are holes on ligand sites (oxygen ions in the case of TM oxides): $d^n + p^6 \rightarrow d^{n+1} + p^5$. MHI are usually described by an effective Hubbard model, in which only the d -electron states are considered explicitly. On the other hand, CTI are described by models that include also the relevant oxygen p -states, such as the dp (or three-band Hubbard) model of high- T_c superconductors [2]. The value of the gap is determined by the smallest of the two parameters: the energy of electron transfer from ligand to TM sites Δ and the Hubbard repulsion on TM sites U_d . For CTI (usually, the oxides of heavier $3d$ metals) $\Delta < U_d$, while for MHI $U_d < \Delta$.

The distinction between these two types of insulators becomes apparent upon doping and may play an important role in high- T_c superconductors [2, 3], though according to other point of view, there is no qualitative difference between doped CTI and MHI [4]. In the absence of doping, both CTI and MHI with one electron or hole per TM site are $S = \frac{1}{2}$ Heisenberg antiferromagnets.

The situation turns out to be quite different in Jahn-Teller systems, in which d -electrons, in addition to spins, have also orbital degrees of freedom. In this Letter we show that in insulators with orbital degeneracy not only the excitation spectrum, but also an orbital and magnetic ordering in the ground state may strongly depend on the ratio Δ/U_d . The difference between the ground states of CTI and MHI results from a peculiar exchange interaction between orbitals on nearest-neighbor d -sites, which may be called ‘the orbital Casimir force’, as it originates from the vacuum energy of charge fluctuations due to the hopping of electrons between the ligand and TM ions (whereas the usual exchange involves the electron trans-

fer from one TM site to another). We recently noted the importance of such interaction in geometrically frustrated systems with the 90° metal-oxygen-metal bonds, e.g. NaNiO_2 , where it determines the type of orbital ordering [5]. Here we show that this orbital exchange of electronic origin is generally present in all TM oxides and, in particular, in materials with the 180° metal-oxygen-metal bonds, like perovskites ABO_3 and their layered analogs A_2BO_4 , and it is not included in the widely used exchange model [6, 7] (sometimes called Kugel-Khomskii (KK) model). That model is derived from an effective Hubbard model describing only the degenerate d -electron orbitals and which, strictly speaking, only applies to MHI with $\Delta \ll U_d$. The new orbital interaction obtained below helps to resolve a difficulty of the KK model, in which an orbital ordering is strongly coupled to a magnetic one, implying close temperatures of orbital and magnetic orderings [7], whereas in reality orbitals usually order at higher temperatures than spins.

Exchange interactions: We first calculate an exchange Hamiltonian for two TM ions with one hole on the doubly degenerate e_g -level, e.g. Cu^{2+} ($t_{2g}^6 e_g^3$). The two orthogonal e_g -orbitals $|3z^2 - r^2\rangle$ and $|x^2 - y^2\rangle$ may be described by, respectively, the up and down states of the isospin- $\frac{1}{2}$ operator T^z [6, 7]. It is convenient to introduce an overcomplete set of operators $d_{i\alpha\sigma}$ on each TM site i annihilating a hole in the state $|3\alpha^2 - r^2\rangle$ ($\alpha = x, y, z$) with the spin projection σ . These states are hybridized with the p_α orbitals on two neighboring oxygen sites $i \pm \frac{\alpha}{2}$ (the corresponding oxygen hole operators are denoted by $p_{i \pm \frac{\alpha}{2}, \sigma}$). The hole states on TM sites are described by the standard atomic Hamiltonian, which includes the on-site repulsion U_d and the Hund’s rule exchange coupling J_d for holes on two orthogonal orbitals. The Hamiltonian of oxygen holes hybridized with the d -states is

$$H_p = H_{kin} + U_p \sum_{i,\alpha} p_{i+\frac{\alpha}{2}}^\dagger p_{i+\frac{\alpha}{2}} p_{i+\frac{\alpha}{2}}^\dagger p_{i+\frac{\alpha}{2}} + t_{pd} \sum_{i,\alpha,\sigma} \left[d_{i\alpha\sigma}^\dagger (p_{i+\frac{\alpha}{2},\sigma} + p_{i-\frac{\alpha}{2},\sigma}) + h.c. \right] \quad (1)$$

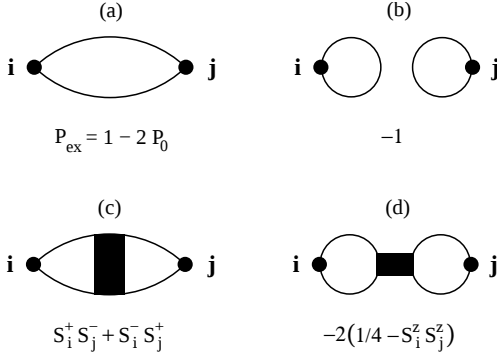


FIG. 1: Diagrams describing exchange interactions mediated by two virtual oxygen holes.

where the first term is the kinetic energy of holes in the oxygen p -band, the second term is the Hubbard repulsion on oxygen sites, and the last term describes the hopping between oxygen and TM sites.

Integrating the oxygen degrees of freedom out, one obtains an effective interaction between d -electrons in the form of an expansion in powers of $(t_{pd}/\Delta)^2$. The lowest order term provides a hopping between TM sites, which together with the Coulomb and Hund's rule interactions between d -electrons gives an effective dd -model. For dispersionless oxygen holes, $H_{kin} = \Delta \sum_{i,\alpha,\sigma} p_{i+\frac{\alpha}{2}\sigma}^\dagger p_{i+\frac{\alpha}{2}\sigma}$, the effective dd -hopping occurs between nearest-neighbor TM sites, and its amplitude is $t_{dd} = t_{pd}^2/\Delta$.

The next term in this expansion ($\propto t_{pd}^4$) gives an orbital and spin exchange mediated by two oxygen holes. The corresponding diagrams are shown in Fig.1, where in the diagrams (a) and (b) two holes do not interact with each other in the virtual state, while the black squares on diagrams (c) and (d) correspond to one or more Hubbard interactions on oxygen sites. Each diagram gives rise to a particular form of spin and orbital exchange. Thus, if the holes on the TM sites i and j exchange places [Fig.1(a)], the spin exchange is described by operator $P_{ex} = +1$ if the total spin of the two holes $S = 1$, and -1 for $S = 0$. This operator can also be written in the form $P_{ex} = 1 - 2P_0$, where $P_0 = 1/4 - (\mathbf{S}_i \mathbf{S}_j)$ is the projector on the $S = 0$ state. If, on the other hand, the holes return back to their starting points, the corresponding 'spin factor' is -1 . The interacting holes in the diagrams (c) and (d) must have opposite spin projections, so the spin exchange in that case is described by $S_i^+ S_j^- + S_i^- S_j^+$ [see Fig.1(c)], while if the spin projections remain unchanged [see Fig.1(d)], the spin operator is $-2(1/4 - S_i^z S_j^z)$. Since the diagrams (c) and (d) only differ by the spin factors, their sum is proportional to $-2P_0$, corresponding to the fact that the on-site Hubbard interaction between two holes is only nonzero when their spins add to the total spin 0.

While the spin-dependence of the exchange interactions, discussed above, is very general, the orbital struc-

ture depends on the dispersion of holes and on relative positions of the sites i and j . In particular, for dispersionless holes the exchange in order t_{pd}^4 only occurs between two nearest neighbor TM sites, e.g. i and $i + \alpha$, and the diagrams (a), (c), and (d) are proportional to $\mathcal{I}_{i\alpha} = (\frac{1}{2} + I_i^\alpha)(\frac{1}{2} + I_{i+\alpha}^\alpha)$, where

$$I^x = -\frac{1}{2}T^z - \frac{\sqrt{3}}{2}T^x, I^y = -\frac{1}{2}T^z + \frac{\sqrt{3}}{2}T^x, I^z = T^z, \quad (2)$$

and the operator $(\frac{1}{2} + I_i^\alpha) = d_{i\alpha}^\dagger d_{i\alpha}$ is the projector on the state $|3\alpha^2 - r^2\rangle$ on the site i . The contribution of the diagram in Fig.1(b) is proportional to $4 \sum_{\beta,\gamma} (\frac{1}{2} + I_i^\beta)(\frac{1}{2} + I_j^\gamma) = 9$, since $I^x + I^y + I^z = 0$.

Combining terms containing P_0 with the exchange interactions appearing in the dd -model in the order t_{pd}^4 , we obtain

$$H_{ST} = -\frac{4t_{pd}^4}{\Delta^2} \sum_{i,\alpha} \left[\left(\frac{1}{U_d} + \frac{2}{2\Delta + U_p} \right) \mathcal{I}_{i\alpha} P_0 + \frac{J_d}{2U_d^2} \left(\frac{1}{4} - I_i^\alpha I_{i+\alpha}^\alpha \right) P_1 \right], \quad (3)$$

where the last term describes the Hund's rule coupling on TM sites and $P_1 = 1 - P_0 = 3/4 + (\mathbf{S}_i \mathbf{S}_j)$ is the projector on the $S = 1$ state. In addition to the coupled spin and orbital interactions, there exists also a spin-independent orbital exchange

$$H_T^{(h)} = \frac{2t_{pd}^4}{\Delta^2} \sum_{i,\alpha} \left[\frac{1}{\Delta} \left(\frac{1}{2} + I_i^\alpha \right) \left(\frac{1}{2} + I_{i+\alpha}^\alpha \right) - \frac{1}{U_d} \left(\frac{1}{4} - I_i^\alpha I_{i+\alpha}^\alpha \right) \right] \quad (4)$$

The first term is the spin-independent contribution of the processes shown in Figs.1(a) and (b), while the second one results from the dd -model. It is important to note that in the order t_{pd}^4 it is impossible to exchange two holes in such a way that they never occupy the same oxygen site (the corresponding terms in the diagrams (a) and (b) cancel each other). The orbital exchange interaction containing only powers of Δ is actually due to the virtual hopping of holes to all neighboring oxygen sites and back [Fig.1(b)], except for the oxygen bridging the two neighboring TM sites. In the limit $\Delta \gg U_d$ Eqs. (3) and (4) reduce to the KK model.

The term in H_T containing only Δ in denominator is similar to the pure orbital exchange for the 90° metal-oxygen-metal bonds [5], and its origin can be better understood by noting that it is the only term that does not vanish in the limit of infinite on-site Hubbard repulsion U_p and U_d . It represents the energy of the delocalization of holes over the octahedra of the ligand ions, surrounding the TM sites, or more correctly, the increase of that energy due to the fact that the neighboring octahedra

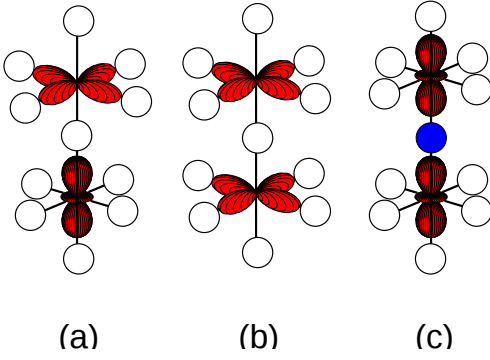


FIG. 2: Favorable [(a) and (b)] and unfavorable (c) occupations of hole orbitals of neighboring TM ions in CTI, in which the exchange is dominated by Eq.(4) (the terms $\propto U_d^{-1}$ stabilize the state (a)).

share one ligand ion and for infinite U_p the intermediate two-hole states on the shared ion are forbidden. This energy increase depends on orbital states of the neighboring holes, which gives rise to the orbital exchange with the positive sign. Thus the origin of this orbital interaction is similar to that of the Casimir effect [8], resulting from the dependence of the energy of zero-point fluctuations of electromagnetic field on positions of two metallic plates. It is also important that this orbital exchange has positive sign, while all other terms in Eqs. (3) and (4) are negative (since they describe the second-order corrections to the ground state energy in the effective dd -hopping). The result of this new orbital interaction can be formulated as the following “rule of thumb” (applied also to materials with one electron per TM site): to avoid the energetically unfavorable occupation of the bridging oxygen by two holes, the d -holes should occupy orbitals directed *away* from the common oxygen either on both neighboring TM sites [see Fig.2(b)] or, at least, on one site [see Fig.2(a)].

The importance of the orbital exchange Eq.(4) for an orbital ordering may be understood already by considering the minimal-energy states of a pair of holes on the neighboring TM sites i and $i+z$. In MHI ($\Delta > U_d$) the exchange is dominated by H_{ST} (3) and the last term in Eq.(4). The AFM exchange between spins of the holes, described by this term, is the strongest for $I^z = \frac{1}{2}$ on both sites, i.e., the lowest energy is achieved if both holes occupy the $|3z^2 - r^2\rangle$ state, as shown in Fig.2(c). The ground state of the pair is a spin singlet. On the other hand, in CTI ($\Delta < U_d$) the strongest interaction is the orbital exchange H_T (see Eq.(4)), and the state shown in Fig.2(c) has the highest orbital energy, since both hole orbitals are oriented towards the common ligand ion. The more energetically favorable states in CTI will be those, in which at least one hole is in the $|x^2 - y^2\rangle$ state (see Fig.2a and b). Furthermore, both the last term in Eq.(4) and the relatively weak FM spin exchange due to the

Hund’s rule coupling select the state shown in Fig.2a with the total spin of the pair $S = 1$. Thus, the ground state of the pair in the CT regime is *different* from that in the MH regime.

Consider now two neighboring TM sites with one e_g electron, as e.g. Mn^{3+} ($t_{2g}^3 e_g^1$), Cr^{2+} ($t_{2g}^3 e_g^1$), and the low-spin Ni^{3+} ($t_{2g}^6 e_g^1$). In the KK model the systems with 1 electron/site and 1 hole/site order in exactly the same way, since the Hubbard model, from which the KK exchange Hamiltonian is derived, has the electron-hole symmetry [7]; consequently, the term H_{ST} (3) has the same form both for electrons and holes. On the other hand, in the dp -model this symmetry is lost: the new orbital exchange interaction for one-electron case has the form [cf. Eq.(4)]

$$H_T^{(e)} = + \frac{2t_{pd}^4}{\Delta^2} \sum_{i,\alpha} \left[\frac{1}{\Delta} \left(\frac{3}{2} - I_i^\alpha \right) \left(\frac{3}{2} - I_{i+\alpha}^\alpha \right) - \frac{1}{U_d} \left(\frac{1}{4} - I_i^\alpha I_{i+\alpha}^\alpha \right) \right] \quad (5)$$

In this case for both MHI and CTI the energy of a pair of TM electrons on the sites i and $i+z$ is minimal if both electrons occupy the $d_{3z^2-r^2}$ orbital, Fig.2(c), and their spins form the singlet state.

Note that the electron-phonon (Jahn-Teller) interaction also gives rise to a purely orbital exchange of the form $H_{JT} \propto \sum_{i,\alpha} I_i^\alpha I_{i+\alpha}^\alpha$, which for both the electron and hole cases favors the antiferro-orbital (AFO) spin-triplet state shown in Fig.2(a). Thus the JT interaction favors the same state as the novel orbital exchange for one-hole systems, but a different one for one-electron systems. This, in principle, gives a possibility to experimentally discriminate between these two mechanisms and to study their relative importance. The Cu^{2+} pairs (one hole) in K_2ZnF_4 were found to have the triplet ground state [9], showing that the orbital exchange Eq.(4) and/or JT interaction are in this case stronger than the KK exchange. We are not aware of similar data for pairs of one-electron ions.

Orbital and magnetic ordering: Equations (3–5) allow us to consider types of ordering in different situations. Thus, e.g., the ground state of a chain of TM ions in the z -direction with 1 hole/site is AFO with alternating $d_{3z^2-r^2}$ and $d_{x^2-y^2}$ orbitals and FM for CTI, as that is favored by the sum of Eqs. (3) and (4), while for MHI, in which H_{ST} dominates, we obtain the ferro-orbital ordering with $d_{3z^2-r^2}$ orbitals occupied on all sites, and the AFM spin exchange [14]. The latter state also minimizes the exchange energy of one-dimensional CTI with 1 electron/site.

Similarly e.g. for CTI ($U_d \rightarrow \infty$) with a square lattice and 1 hole/site, the orbital exchange interaction Eq.(4) has the form

$$H_T = + \frac{2t^4}{\Delta^3} \sum_i (I_i^x I_{i+x}^x + I_i^y I_{i+y}^y - I_i^z). \quad (6)$$

The term bi-quadratic in isospin operators favors an antiparallel orientation of neighboring isospins, while the linear term in Eq.(6) acts as ‘the orbital field’ in the z direction, favoring the canted orbital state with the canting angle $\pm 60^\circ$, which corresponds to the two-sublattice orbital ordering with the $d_{z^2-x^2}$ and $d_{z^2-y^2}$ hole states. Since these two neighboring orbitals do not overlap, the Hund’s rule coupling (the last term in Eq.(3)) results in the FM exchange between the spins of the holes. This is precisely the orbital and magnetic structure of the layered compound K_2CuCl_4 . For MHI, however, we would get from Eq.(3) a different ground state: ferro-orbitally ordered with $I^z = -\frac{1}{2}$ ($d_{x^2-y^2}$ -orbitals) and AFM spin ordering (see, however, Ref. 14). Previously, the KK model was successfully used to predict the orbital structure of that compound [10], *assuming* that spins order ferromagnetically; but as we mentioned above, such a state is not the ground state of the KK model.

The case of a cubic lattice of TM ions is somewhat special for several reasons. First, using $\sum_\alpha I_i^\alpha = 0$, we find that the exchange interactions have the electron-hole symmetry. In particular, both Eq.(4) and Eq.(5) can be written in the form

$$H_T = +\frac{2t^4}{\Delta^2} \left(\frac{1}{\Delta} + \frac{1}{U_d} \right) \sum_i (I_i^x I_{i+x}^x + I_i^y I_{i+y}^y + I_i^z I_{i+z}^z). \quad (7)$$

Second, the orbital interaction Eq.(7) is frustrated [11, 12]: apart from the AFO mean-field ground states with the average isospin vector $\langle \mathbf{T}_i \rangle$ parallel (antiparallel) to an arbitrary vector in the (T^x, T^z) -plane, there are infinitely many disordered ground states, obtained from the AFO states by performing the transformation $I^\alpha \rightarrow I^\gamma$, $I^\beta \leftrightarrow I^\gamma$, where α, β , and γ are three different spatial indexes, on an arbitrary set of planes transverse to the α axis. This ground state degeneracy is similar to the one of the orbital Hamiltonian of e_g electrons on a triangular lattice [5]. The quantum orbital fluctuations select the AFO states $I^\alpha = \pm \frac{1}{2}$, where $\alpha = x, y$ or z , which have the softest (two-dimensional) orbital excitations [12]. For instance, for $\alpha = z$, such a state corresponds to the occupation of $d_{3z^2-r^2}$ and $d_{x^2-y^2}$ orbitals on A and B sublattices. The corresponding magnetic ordering would be AFM in the xy planes and FM in the z direction.

If we now would increase the ratio Δ/U_d , moving from CTI to MHI, the coupling between orbitals and spins would ultimately stabilize the canted AFO state with an AFM coupling along the chains in the z direction and a FM exchange between spins in the xy layers. The detailed treatment of this case, relevant e.g. for the perovskites KCuF_3 and LaMnO_3 , will be given elsewhere.

In conclusion, we showed that the description and properties of orbital ordering in charge transfer insulators are much different from those in Mott-Hubbard in-

ulators. In particular, even in perovskite CTI with the 180° -exchange the orbital interactions are stronger than the spin exchange, so that an orbital ordering, in general, occurs at higher temperatures. In this respect the exchange mechanism of an orbital ordering in CTI resembles the ordering due to the JT (electron-phonon) interaction, although is not identical to it. Another difference between the CTI and MHI is that the electron-hole symmetry existing in the MH case is lost in the CT regime, so that the type of an orbital and spin ordering may be different for one-electron and one-hole materials. The effective exchange Hamiltonian for CTI allows us to describe the ordering in a number of such materials, without invoking any extra factors. Most importantly, in orbitally degenerate insulators not only the excitation spectrum, but also the very type of the ground state may be different in Mott-Hubbard and charge transfer regimes, in contrast to the non-degenerate case, in which it is the same.

This work was supported by the MSC^{plus} program and the Stichting voor Fundamenteel Onderzoek der Materie (FOM).

-
- [1] J. Zaanen, G.A. Sawatzky, and J.W. Allen, Phys. Rev. Lett. **55**, 418 (1985).
 - [2] V.J. Emery, Phys. Rev. Lett. **58**, 2794 (1987).
 - [3] C.M. Varma, Phys. Rev. Lett. **83**, 3538 (1999).
 - [4] F.C. Zhang and T.M. Rice, Phys. Rev. B **37**, 3759 (1988).
 - [5] M.V. Mostovoy and D.I. Khomskii, Phys. Rev. Lett. **89**, 227203 (2002).
 - [6] K.I. Kugel and D.I. Khomskii, Sov. Phys. JETP **52**, 501 (1981);
 - [7] K.I. Kugel and D.I. Khomskii, Sov. Phys. Uspekhi **25**, 232 (1982).
 - [8] H.B.G. Casimir, Proc. Kon. Ned. Akad. Wetensch. B **51**, 793 (1948).
 - [9] M.V. Eremin, Yu.V. Yablokov, T.A. Ivanova, and R.M. Gumerov, Sov. Phys. JETP **60**, 128 (1984).
 - [10] D.I. Khomskii and K.I. Kugel, Solid State Commun. **13**, 763 (1973).
 - [11] L. F. Feiner, A. M. Oles, and J. Zaanen, Phys. Rev. Lett. **78**, 2799 (1997).
 - [12] G. Khaliullin, Phys. Rev. B **64** 212405 (2001).
 - [13] J.E. Medvedeva, M.A. Korotin, V.I. Anisimov, and A.J. Freeman, Phys. Rev. B **65**, 172413 (2002).
 - [14] These conclusions may be modified, if we include anharmonicity effects, considered e.g. by D. I. Khomskii and J. van den Brink, Phys. Rev. Lett. **85**, 3329 (2000). In low-dimensional systems the orbital degeneracy may be also lifted by the symmetry of the crystal structure, which results in the term $H' = \lambda \sum_i I_i^z$, for the one-dimensional chains along the z axis and for the two-dimensional xy planes.